

BEST AVAILABLE COPY

DECLASSIFIED

(CLASSIFICATION)

DOCUMENT NO.

H.V-8899

SERIES AND COPY NO.

GENERAL ELECTRIC

HANFORD ATOMIC PRODUCTS OPERATION - RICHLAND, WASHINGTON

DATE
2-17-48

~~RESTRICTED DATA~~
THIS DOCUMENT CONTAINS RESTRICTED DATA AS
DEFINED IN THE ATOMIC ENERGY ACT OF 1954.
ITS TRANSMITTAL OR DISCLOSURE OF ITS
CONTENTS IN ANY MANNER TO AN UNAUTHORIZED
PERSON IS PROHIBITED.

TITLE

TRIP TO MORGANTON PLANT OF THE
NATIONAL CARBON COMPANY

☐ OTHER OFFICIAL CLASSIFIED INFORMATION
THIS MATERIAL CONTAINS INFORMATION AFFECTING
THE NATIONAL DEFENSE OF THE UNITED STATES
WITHIN THE MEANING OF THE ESPIONAGE LAWS,
TITLE 18, U.S.C., SECS. 793 AND 794, THE TRANS-
MISSION OR REVELATION OF WHICH IN ANY MANNER
TO AN UNAUTHORIZED PERSON IS PROHIBITED BY
LAW.

AUTHOR

C. W. BOTSFORD

CIRCULATING COPY
RECEIVED 300 AREA

15 1958

RETURN 10

TECHNICAL INFORMATION FILES

THIS DOCUMENT MUST NOT BE LEFT UNATTENDED OR WHERE AN UNAUTHORIZED PERSON MAY HAVE ACCESS
TO IT. WHEN NOT IN USE, IT MUST BE STORED IN AN APPROVED LOCKED REPOSITORY WITHIN AN APPROVED
GUARDED AREA. IT IS YOUR RESPONSIBILITY TO KEEP IT AND ITS CONTENTS WITHIN THE LIMITS OF
CLASSIFICATION. IT IS YOUR RESPONSIBILITY TO KEEP IT AND ITS CONTENTS WITHIN THE LIMITS OF
THIS ACT AND FROM ANY UNAUTHORIZED PERSON. ITS TRANSMITTAL TO, AND STORAGE AT YOUR PLACE
OF RESIDENCE IS PROHIBITED. IT IS NOT TO BE REPRODUCED. IF ADDITIONAL COPIES ARE REQUIRED,
OBTAIN THEM FROM THE ISSUING FILE. ALL PERSONS READING THIS DOCUMENT ARE REQUESTED
TO SIGN IN THE SPACE PROVIDED BELOW.

ROUTE TO:

C E LOVE

PAYROLL NO.

12534

LOCATION

703 D

FILES ROUTE
DATE

10-15-58

SIGNATURE AND DATE

C. E. Love 3/12/60
J. A. Collins 1/10/60

DECLASSIFIED

1st REVIEW-DATE:

AUTHORITY AOC ADC ADD

NAME

ORG

2nd REVIEW-DATE: 12/9/72

NAME: BT O'Meara

ORG

APPROVED FOR
PUBLIC RELEASE

DECLASSIFIED

C-3193-MB (7 - 58) AEC-GE-RICHLAND, WASH

(CLASSIFICATION)

RECEIVED

MAY 21 1956

300 AREA
CLASSIFIED FILES

DECLASSIFIED

DECLASSIFIED

RW-8899

- # 1 - A. B. Greninger
- # 2 - D. H. Lander - G. C. Lail - *Chen*
- C. N. Gross - 700 File
- # 3 - C. W. J. Wende
- # 4 - W. K. Woods
- # 5 - P. F. Gast - J. M. West
- # 6 - C. W. Botaford
- # 7 - H. A. Fowler
- # 8 - R. M. Kenady
- # 9 - J. E. Maider - E. F. Lee
- # 10 - W. I. Patnode - 300 File
- # 11 - Pink Copy
- # 12 - Yellow Copy

C.E. Jones #1234 RECORD COPY

February 17, 1948

TO: File

THIS DOCUMENT CONSISTS OF 3 PAGE(S)

FROM: C. W. Botaford

C. W. Botaford, 300 AREA, BIRMINGHAM

SUBJECT: Trip to Morganton Plant of the National Carbon Company

Object of Trip: The Morganton Plant of the National Carbon Company was visited on January 26 through January 29 to observe the graphite purification process. The object of the trip was to study the purification operation to obtain as much general information as possible regarding the process, and to follow up the sampling and sample shipments of the initial purification runs.

Description of Process: The purification process involves the conversion of graphite impurities, probably present in solid solution in the graphite, into volatile halides which are swept from the graphite by means of nitrogen. The impurities present are Si, Al, K, Ca, V, B, and others, and are probably present in the graphite due to their accumulation in the still bottoms and producer gas furnace tars from which the coke and pitch in the graphite are made.

The purification is accomplished in a converted Acheson graphitizing furnace in which sixty-eight bars of graphite are placed on a thin bed of pure carbon coke. Individual graphite gas distributor tubes are placed in the coke bed beneath the graphite bars. The bars and the small space between each bar are covered lightly with pure coke. Three carbon electrodes at each end of the furnace are in contact with the resistance coke and carry the heating current. A current in excess of 20,000 amps heats the bed to 2400° C. The gas distributor tubes are connected to a common distributor pipe which runs alongside the furnace. The entire furnace is sealed from the atmosphere by means of a ceramic sheet cover under which a slight vacuum is maintained to prevent contamination of the room with noxious gases formed in the furnace.

The purifying gas used is CCl_4 at temperatures below 2000° C. and $\text{CCl}_4\text{-F}_2$ at temperatures above 2000° C. Nitrogen gas is fed to the furnace at all times. The heating cycle requires from 4 to 5 hours while the cooling cycle is approximately 24 hours. The furnace is above 2000° C. approximately 5 hours during which time $\text{CCl}_4\text{-F}_2$ is fed. The CCl_4 is fed as a gas at the heating cycle below 2000° C. and on the cooling cycle from 2000° C. to 1000° C. Nitrogen flow is maintained for 6 hours after the CCl_4 flow has been cut off to insure sweeping the noxious gases from the bed. The gases are scrubbed by a caustic solution in a scrubber current column packed with Raschig rings before being vented to the atmosphere.

DECLASSIFIED


DECLASSIFIED

DECLASSIFIED

HN-8899

-2-

The curve below shows the approximate conditions of a standard purification run.

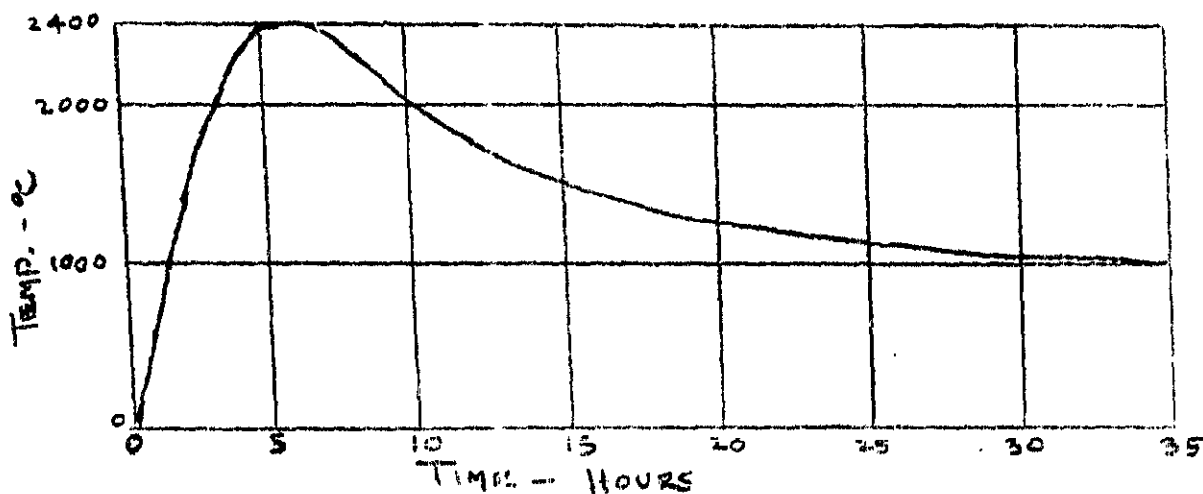

Nitrogen gas feed: 100 cu. ft./hr.
 F_{12} feed: 50 lbs/hr
 CCl_4 approximately 25 cu. ft./hr.

The CCl_4 is introduced by passing the N_2 through a long tube partially filled with liquid CCl_4 and heated to maintain a partial pressure of 140 mm.

The CCl_2F_2 must be introduced at elevated temperatures because at low temperatures fluorine formed by pyrolysis of CCl_2F_2 reacts with the graphite causing structural failure of the graphite. It is the belief of the United Carbon Company and the National Carbon Company people that all of the impurities of the graphite are removed on the heating cycle and that the CCl_4 feed on the cooling cycle is superfluous.

One Acheson furnace was converted for purification on February 1 and four more furnaces are being converted. All five units should be in operation by February 28. The complete furnace cycle requires about six days which should result in one complete heat per day when all furnaces are in operation.

Recommendations Made: The original cooling cycle used by United Carbon called for cooling down to 800° C. before stopping the CCl_4 feed. It was recommended that on the second run the CCl_4 feed be stopped at 1000° C. thus saving about eight hours on the cooling cycle. It was further recommended that the CCl_4 feed be stopped still earlier if the test results indicate no decrease in reactivity.

The writer conferred with Mr. R. M. Kennedy of the Construction Department on the graphite bar specifications and found that in view of the reduced size bars used to support the process tubes most of the bars currently being culled could be used, thereby effecting a considerable saving.

There appear to be several avenues open toward further process improvements. These may be summarized as follows:

1. Control of temperature cycle. At present, the temperature cycle is governed primarily by the power cycle. Pyrometer readings were taken at only one location. It is now known that considerable variations in quality occur

DECLASSIFIED

